

Plain and Reinforced Concrete Laboratory Civil Engineering Department

University of Engineering and Technology, Lahore. Pakistan Landline: 042-99029245 & 042-99029202 Mobile: 0307-0496895 ORIGINAL A carbon copy for the report has been retained in the lab for record.

2930 Dr. Umbreen

To: Muhammad Saleem Awan, FM (Works Div) SRDC-L SUPARCO Office Works Division P.O. Punjab University Samsani Road, Lahore.

Project: Construction of MTVC Facility at SRDC-L. (M/s Malik Builders & Company).

Our Ref. No. CL	/CED/ 8272	Dated:	14-03-22	Test Specification
Your Ref. No.	63302(MTVC) Works/Div/SRDC-L	Dated:	25-02-22	(ASTM C39)

COMPRESSION TEST REPORT

Specim	ens received on:	1	1-03	-22	Tested on:	14-()3-22	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		-	Date*	Size (in)	Wet Weight (Ka/ ams)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)			Water Absorpti on (%)	Remarks
1	RCC Roof Slab (3500 Psi)	13	1	2022	6Diax12		13.6	28.28	65	5149		Engraved
2	RCC Roof Slab (3500 Psi)	13	1	2022	6Diax12		13	28.28	61	4832		Engraved
3												
4												
5					/	RINE	RIATE					
6					>	T READ W	RIFT					
7						DHE NAME <u>OE</u> THY LORD WHO	4	EB				
8					4.81			IN D				
9						×	- 5	7				
10					<	-14	IORE .					
11												
12												
13												
14												
15												
16												
Witness	sed by: Nil											

Witnessed by: Nil

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory



ORIGINAL A carbon copy for the report has been retained in the lab for record.

2863 Dr. Umbreen

To:	: Mehmood Iqbal Cheema, Resident Engineer Engineering Consultancy Services (Pvt) Limited, Lahore.											
	Project: Infrastructure Development and Construction of Affordable Housing Units at Moza Rakh Paji, Tehsil Raiwind, District Lahore. (Contract No. AHU/333/01)											
	Our Ref. No. CL/	CED/ 8273	Dated:	14-03-22	Test Specification							
	Your Ref. No.	ECSP/RE/LH/32	Dated:	25-02-22	(BS 3921**)							

COMPRESSION TEST REPORT



Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	0	2-03	-22	Tested on:	14-0)3-22	in dry/we	t condition			
Sr. No.	Mark*		•	Date* YYYY	Size (in)	Wet Weight (Ka/ ams)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)	Ultimate load (Imp.Tons)		Water Absorpti on (%)	Remarks
1	ASW				9 x 4.4 x 2.9	3810	3490	39.6	41	2319	9.17	Fly Ash Brick
2	ASW				9 x 4.4 x 2.8	3795	3450	39.6	35	1980	10	Fly Ash Brick
3	ASW				9 x 4.4 x 2.8	3745	3435	39.6	43	2432	9.02	Fly Ash Brick
4	ASW				9 x 4.4 x 2.9	3955	3590	39.6	55	3111	10.17	Fly Ash Brick
5	ASW				9 x 4.4 x 2.8	3760	3420	39.6	39	2206	9.94	Fly Ash Brick
6						READ IN	205 D					
7						DHE NAME OF THY LORD VIVIO	- E					
8					128			i Na				
9												
10						(A	INR E .					
11												
12												
13												
14												
15												
16												
Witness	sed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory



ORIGINAL
A carbon copy for
the report has
been retained in
the lab for record.

2933 Dr. Yousaf

To: Mr. Babar Ali, Construction Manager For Guarantee Engineers (Pvt.) Ltd. Lahore.

Project: Beaconhouse School System TNS 2.0 Gulberg-iii, Lahore.

Our Ref. No. CL	/CED/ 8274	Dated:	14-03-22	Test Specification
Your Ref. No.	GEPL/TNS2/05/2022	Dated:	13-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	1	4-03	-22	Tested on:	14-0)3-22	in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*		-	Date*	Size (in)	Wet Weight (Ka/ ams)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)	Ultimate load (Imp.Tons)		Water Absorpti on (%)	Remarks
1	Lab No. BH-35 (4000 Psi)	7	2	2022	6Diax12		14	28.28	47	3723		Non Engraved
2	Lab No. BH-35 (4000 Psi)	7	2	2022	6Diax12		13.8	28.28	53	4198		Non Engraved
3	Lab No. BH-35 (4000 Psi)	7	2	2022	6Diax12		14	28.28	53	4198		Non Engraved
4												
5					/	ARTINE	RIATE					
6						I READ W	200 D					
7						DHE NHOLE OF THY LORID WHO		EB				
8					- 188			NND I				
9						×	5	7				
10					<	- LA	INRE.					
11												
12												
13												
14												
15												
16												
Witness	ed by: Mr. M. Ali	Khan	(CN	IC # 33	3100-2629451-	1)						

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory



To: **Consultant, Takbeer Tower** Mecload Road, Lahore.

Project: Nil			
Our Ref. No. CL/CED/ 8275	Dated:	14/3/2022	Test Specification
Your Ref. No. Nil	Dated:	10-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	10	/03/2	2022	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*			Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)			Water Absorpti on (%)	Remarks
1	Raft	27	2	2022	6Diax12		13	28.28	43	3406		Engraved
2	Raft	27	2	2022	6Diax12		13	28.28	41	3248		Engraved
3												
4												
5					-	RINE	RIATE	-				
6						I READ IN						
7						DHE NHOLE <u>OE</u> THY LORD VIND	14.9	EP				
8					188							
9					-	-						
10					-	(A	INR E					
11												
12												
13												
14												
15												
16												
Witness	Witnessed by:											

illiesseu by

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory



Project: Construction of Orchard Mall, Bahria Orchard Lahore.

Our Ref. No. CL	/CED/ 8276	Dated:	14/3/2022	Test Specification
Your Ref. No.	QLC-BO-BH2-2022-03-LTR-07	Dated:	07-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	8/	03/2	022	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	Grid # 18-24 (3000 psi)	7	2	2022	6Diax12		13	28.28	35	2772		Non Engraved
2	Grid # 18-24 (3000 psi)	7	2	2022	6Diax12		12.4	28.28	35	2772		Non Engraved
3	Grid # 18-24 (3000 psi)	7	2	2022	6Diax12		13	28.28	37	2931		Non Engraved
4												
5					/	HEINE	RIATE					
6)	MEAD IN	PAUS D					
7						DHE NAME OF THY CORD VAND		F				
8					188							
9							-					
10						-LA	INRE .					
11												
12												
13												
14												
15												
16												
Witness	sed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as comprensive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



To:	Project Manager.
-----	------------------

Q-Links Property Management Pvt. Ltd.

Project: Construction of Jasmine Grand Mall, Bahria Town, Lahore.

Our Ref. No. CL	/CED/ 8277	Dated:	14/3/2022	Test Specification
Your Ref. No.	QLC-BO-BH2-2022-03-LTR-06	Dated:	07-03-22	(ASTM C39)

COMPRESSION TEST REPORT



Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	8/	03/2	022	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	5500 Psi	5	2	2022	6Diax12		13.2	28.28	59	4673		Engraved
2	3750 Psi	5	2	2022	6Diax12		13	28.28	51	4040		Engraved
3	5500 Psi	7	2	2022	6Diax12		13.2	28.28	49	3881		Engraved
4												
5					/	GINE	RIATE					
6)	I NEAD W	RIAN					
7						DHE NAME CE THY LORD WHO		EB				
8					/ ASI			HND.				
9												
10						- (A	INR E .					
11												
12												
13												
14												
15												
16												
Witness	sed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory



ORIGINAL A carbon copy for the report has been retained in the lab for record.

2909 Dr. Umbreen

To: **Asif Pervaiz Butt** Resident Engineer, AYQ Developers Pvt. Ltd

Project: Union Complex.			
Our Ref. No. CL/CED/ 8278	Dated:	14/3/2022	Test Specification
Your Ref. No. Nil	Dated:	08-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	8/	03/2	022	Tested on:	14/3	/2022	in dry/we	t condition			
Sr. No.	Mark*		•	Date*	Size	Wet Weight		Area of X-Section		Ultimate Stress	Water Absorpti on (%)	Remarks
				YYYY	. ,		(Kg/ gms)		(Imp.Tons)			N
1	5000 Psi	1	3	2022	6Diax12		13	28.28	69	5465		Non Engraved
2	5000 Psi	1	3	2022	6Diax12		13.6	28.28	65	5149		Non Engraved
3	5000 Psi	1	3	2022	6Diax12		13.2	28.28	73	5782		Non Engraved
4	5000 Psi	1	3	2022	6Diax12		13.4	28.28	67	5307		Non Engraved
5	5000 Psi	1	3	2022	6Diax12	RINE	13.2	28.28	67	5307		Non Engraved
6	5000 Psi	1	3	2022	6Diax12	I READ IN	13	28.28	71	5624		Non Engraved
7					11	DIE NACE CETHY CORD VIND	14.					
8					481							
9						à	- 5	7				
10					<	-14	INRE?					
11												
12												
13												
14												
15												
16												
Witness	sed by:	•		•		·	·					

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



GM Engineering Cotton Web Limited.

Project: Raft foundation of New Office Building

Our Ref. No. CL/CED/ 8279	Dated:	14/3/2022	
Your Ref. No. Nil	Dated:	04-03-22	

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	0	7-03	-22	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		•	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)			Water Absorpti on (%)	Remarks
1	Raft Concrete Pour 1 & 4	16	2	2022	6Diax12		13	28.28	55	4356		Non Engraved
2	Raft Concrete Pour 1 & 4	16	2	2022	6Diax12		13.4	28.28	53	4198		Non Engraved
3	Raft Concrete Pour 1 & 4	16	2	2022	6Diax12		13.2	28.28	43	3406		Non Engraved
4	Raft Concrete Pour 2 & 3	18	2	2022	6Diax12		13.2	28.28	37	2931		Non Engraved
5	Raft Concrete Pour 2 & 3	18	2	2022	6Diax12	RINE	13	28.28	57	4515		Non Engraved
6	Raft Concrete Pour 2 & 3	18	2	2022	6Diax12	I READ IN	13.8	28.28	47	3723		Non Engraved
7		-				DHE NHOLE <u>OE</u> THY LORD WHO	14.9	EB				
8								UNI 				
9						-	1					
10		-			<	(A	ER L					
11		-					-					
12		-										
13												
14												
15												
16												
Witnessed by:												

illesseu by

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as comprensive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory

1. The laboratory is not responsible for sampling, originality and construction conditions (such as mix proportion, w/c ratio, compaction, curing and quality of ingredients) 2. The test results are recommended to be interpreted in the light of above factors by the engineer.



Test Specification (ASTM C39)



Project: Column Cap of New Office Building.

Our Ref. No. CL/CED/ 8280	Dated:	14/3/2022	Test Specification
Your Ref. No. Nil	Dated:	04-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	7/	03/2	022	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		•	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	Column Concrete Pour	24	2	2022	6Diax12		13.6	28.28	67	5307		Engraved
2	Column Concrete Pour	24	2	2022	6Diax12		14	28.28	61	4832		Engraved
3												
4												
5						RINE	RIATE					
6						I READ IN						
7						DHE NAME OF THY LORD WHO	6 fr.	EB				
8					/ 8.81		Contraction of the second	IND				
9							1	Z				
10					<	-14	IDRE .					
11												
12												
13												
14												
15												
16												
Witnessed by:												

illesseu by

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as comprensive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory



Plain and Reinforced Concrete Laboratory

Civil Engineering Department

University of Engineering and Technology, Lahore. Pakistan Landline: 042-99029245 & 042-99029202 Mobile: 0307-0496895

ORIGINAL A carbon copy for the report has been retained in the lab for record.

2874 Dr. Umbreen

To: Mr. Zain Raza

Site Engineer, Office of Mr. Ikhlaq, Lahore.

Project: Nil			
Our Ref. No. CL/CED/ 8281	Dated:	14-03-22	Test Specification
Your Ref. No. Nil	Dated:	03-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	0	3-03	-22	Tested on:	14-0	3-22	in dry/we	t condition			
Sr. No.	Mark*		•	Date*	Size (in)	Wet Weight (Ka/ ams)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	Office 3rd Floor Col. (4000 psi)	26	1	2022	6Diax12		13.4	28.28	45	3564		Engraved
2	Office 3rd Floor Col. (4000 psi)	26	1	2022	6Diax12		13.6	28.28	65	5149		Engraved
3	Office 3rd Floor Col. (4000 psi)	31	1	2022	6Diax12		13.8	28.28	83	6574		Engraved
4	Office 3rd Floor Col. (4000 psi)	31	1	2022	6Diax12		14	28.28	75	5941		Engraved
5					/	HINE	RIATE					
6						READ IN						
7						DHE NAME OF THY LORD WHO	149	HB				
8					- USH		No series	HND				
9							1					
10					- <	- (A	IDRE					
11							-					
12												
13												
14												
15												
16												
Witness	ed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as comprensive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



the report has been retained in the lab for record.

ORIGINAL

2874 Dr. Umbreen

To: Zain Raza

Site Engineer, Office of Mr. Ikhlaq

Project: Nil			
Our Ref. No. CL/CED/ 8282	Dated:	14-03-22	Test Specification
Your Ref. No. Nil	Dated:	03-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:		0	3-03	-22	Tested on:	14-03-22		in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Ka/ ams)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)	Ultimate load (Imp.Tons)	Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	Plaza 3rd Floor Col. (4000 psi)	20	1	2022	6Diax12		14	28.28	55	4356		Engraved
2	Plaza 3rd Floor Col. (4000 psi)	20	1	2022	6Diax12		13	28.28	31	2455		Engraved
3	Plaza 3rd Floor Slab (3000 psi)	29	1	2022	6Diax12		13.4	28.28	47	3723		Engraved
4	Plaza 3rd Floor Slab (3000 psi)	29	1	2022	6Diax12		13.4	28.28	59	4673		Engraved
5						EINE	RIATE					
6					>	NEAD IN	205 D					
7						THE NAME OF THY LORD WHO	-E	E -				
8					, RSI			H Ma				
9							-					
10			-		<	d	INR E .					
11												
12												
13												
14												
15												
16												
Witness	sed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory





•	uction of DHA NEWLIFE Residency App ngineering & Construction Pvt. Ltd. Lah		k Phase II DHA, Lah	ore.
Our Ref. No. CL	• •	Dated:	14/3/2022	Test Specification
Your Ref. No.	G3/DHA-NLD/RE/041	Dated:	05-03-22	(ASTM C39)

COMPRESSION TEST REPORT



Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:		10/03/2022		2022	Tested on:	14/3	/2022	in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	Grid O Line 2-4 & Line 7	8	2	2022	6Diax12		13.6	28.28	77	6099		Non Engraved
2	Grid O Line 2-4 & Line 7	8	2	2022	6Diax12		13	28.28	23	1822		Non Engraved
3	Grid O Line 2-4 & Line 7	8	2	2022	6Diax12		13.8	28.28	57	4515		Non Engraved
4												
5						RINE	RIATE					
6						I HEAD N						
7						DHE NAME OF THY LORD WHO	14.9	EB				
8					, RSI			UNI I				
9						-	1					
10						- (A	ER L					
11							-					
12												
13												
14												
15												
16												
Witness	sed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



•	gineering & Construction Pvt. Ltd. Lahore.			
Our Ref. No. CL/	CED/ 8284	Dated:	14/3/2022	Test Specification
Your Ref. No.	G3/DHA-NLD/RE/042	Dated:	03-05-22	(ASTM C39)

COMPRESSION TEST REPORT



Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:			10/03/2022 To		Tested on:	14/3/	/2022	in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)		Area of X-Section (Sq. in)	Ultimate load (Imp.Tons)	Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	Grid R, Line 5-7	7	2	2022	6Diax12		14	28.28	79	6257		Non Engraved
2	Grid R, Line 5-7	7	2	2022	6Diax12		13.2	28.28	65	5149		Non Engraved
3	Grid R, Line 5-7	7	2	2022	6Diax12		13.2	28.28	55	4356		Non Engraved
4												
5					/	GINE	RIATE					
6)	I NEAD W	2.15					
7					-	DHE NAME OF THY LORD WHO	4					
8					- ASI		the set	I Na				
9							-					
10					<	- (A	IDRE .					
11												
12												
13												
14												
15												
16												
Witness	ed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as comprensive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



To: Engr. Mujtaba Ahmad, Structure Engineer HiSEL Power Pakistan Garden Town, Lahore.

Project: Treet Corporation Pvt. Ltd.			
Our Ref. No. CL/CED/ 8285	Dated:	14/3/2022	Test Specification
Your Ref. No. Nil	Dated:	11-03-22	(BS 1881-116)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:		11/03/2022		2022	Tested on:	14/3/2022		in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*		•	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1	SP1	11	12	2021	6x6x6		7.4	36	65	4044		Non Engraved
2	SP2	17	12	2021	6x6x6		7.2	36	51	3173		Engraved
3	SP3	23	12	2021	6x6x6		8	36	94	5849		Non Engraved
4												
5					/	GEINE	RIATE					
6)	I READ IN	San De					
7						DHE NIGHE OF THY LORD WHO	14.4					
8					- SH			IND.				
9						à		,				
10					<	LA	INRE .					
11												
12												
13												
14												
15												
16												
Witness	sed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory

1. The laboratory is not responsible for sampling, originality and construction conditions (such as mix proportion, w/c ratio, compaction, curing and quality of ingredients) 2. The test results are recommended to be interpreted in the light of above factors by the engineer.



ORIGINAL A carbon copy for the report has been retained in the lab for record.

2929 Dr. Umbreen



2928 Dr. Umbreen

To: Engr. Abdul Abdul Basit Vision Developers (Pvt.) Ltd. Gulberg-III, Lahore.

Project: SAMAA TV Office			
Our Ref. No. CL/CED/ 8286	Dated:	14/3/2022	Test Specification
Your Ref. No. VD/CP/003/10032022	Dated:	10-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specim	ens received on:	11/03/2022		022	Tested on:	14/3	/2022	in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)			Water Absorpti on (%)	Remarks
1	3000 Psi	10	2	2022	6Diax12		13.6	28.28	53	4198		Engraved
2	3000 Psi	10	2	2022	6Diax12		13.4	28.28	47	3723		Engraved
3	3000 Psi	10	2	2022	6Diax12		13.6	28.28	61	4832		Engraved
4												
5					/	GINE	RIATE					
6)	READ IN	200					
7						DHE NAME CE THY LORD WHO	4	HE				
8					ASI RSI			IND				
9						×	-	7				
10					<		IDRE .					
11												
12												
13												
14												
15												
16												
Witness	ed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory





Engr. Abdul Qadeer Khan LANDMARK CONSULTANTS Gulberg-II Lahore.

Project: Parkview Apartments.			
Our Ref. No. CL/CED/ 8287	Dated:	14/3/2022	Test Specification
Your Ref. No. CIV/172/07032022	Dated:	07-03-22	(ASTM C39)

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:			10/03/2022		Tested on:	14/3	/2022	in dry/wet condition				ONLINE REPORT
Sr. No.	Mark*	Cas DD	-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)		Ultimate Stress (psi)	Water Absorpti on (%)	Remarks
1		28	2	2022	6Diax12		14	28.28	49	3881		Non Engraved
2		28	2	2022	6Diax12		14	28.28	67	5307		Non Engraved
3		28	2	2022	6Diax12		14	28.28	41	3248		Non Engraved
4												
5					/	GINE	RIATE					
6					>	NEAD W	200					
7					11	DE NICE CE THY LORD WHO	-4					
8					4.81			IND				
9						×						
10					<	-14	IORE .					
11												
12												
13												
14												
15												
16												
Witness	sed by:											

To:

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



Innovative Construction Company, Lahore.

Project: Construction of ABL Branch at Jubilee Town, Lahore.

Our Ref. No. CL	/CED/ 8288	Dated:	14/3/2022	Test Specification
Your Ref. No.	ICL/ABL/JT/0322/04	Dated:	02-03-22	()

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:		0	3-02	-22	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		•	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)			Water Absorpti on (%)	Remarks
1	А				8.7 x 4.3 x 2.9		3055	37.41	37	2215		
2	А				8.6 x 4.2 x 2.8		3095	36.12	55	3411		
3	А				8.5 x 4.2 x 2.9		3105	35.7	49	3075		
4												
5					/	RINE	RIATE					
6)	I READ W	PART N					
7						DHE NAKE	4					
8					- SA			NND N				
9						2-		X				
10					- <	-14	ORE					
11												
12												
13												
14												
15												
16												
Witness	Witnessed by:											

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/


1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as comprensive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory

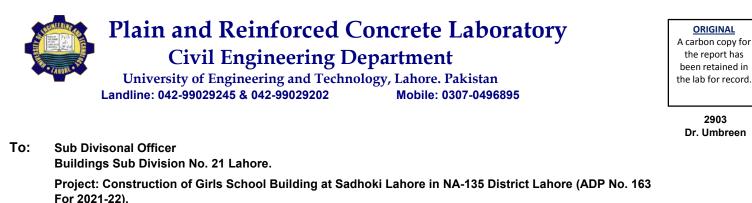

Our Ref. No. CL/CED/ 8289	Dated:	14/3/2022	Test Specification
Your Ref. No. 26/21	Dated:	26/1/2022	()

COMPRESSION TEST REPORT

Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:		0	7-03	-22	Tested on:	14/3	/2022	in dry/we	t condition			ONLINE REPORT
Sr. No.	Mark*		-	Date* YYYY	Size (in)	Wet Weight (Kg/ gms)	Dry Weight (Kg/ gms)	Area of X-Section (Sq. in)			Water Absorpti on (%)	Remarks
1	RA				8.9 x 4.3 x 3		3400	38.27	43	2517		
2	RA				8.9 x 4.4 x 3		3380	39.16	37	2116		
3	RA				9 x 4.4 x 3		3585	39.6	33	1867		
4												
5					/	GINE	RIATE					
6					>	HEAD W	200					
7						DHE NAME CE THY LORD WHO	4	EC				
8					/ RSI			HN0				
9							1	X				
10					<	-//	IORE .					
11												
12												
13												
14												
15												
16												
Witnessed by:												

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

Note: Above results pertain to the unsealed samples supplied to the laboratory



ORIGINAL							
A carbon copy for							
the report has							
been retained in							
the lab for record.							

2773 Dr. Umbreen

To: **Sub Divisonal Officer**

Changa Manga Sub Division Changa Manga.

Project: Concrete Side Protection of VAHN Disty From RD 0+000 TO 36+055 (Package-A).

Our Ref. No. CL	/CED/ 8290	Dated:	14/3/2022	Test Specification
Your Ref. No.	249/IE/VAHN	Dated:	06-02-22	(BS 3921**)

COMPRESSION TEST REPORT



Concrete Cubes/Concrete Cylinders/Bricks/Cores/Tuff Tiles/Pavers

Specimens received on:		0	7-03	-22	Tested on:	14/3	/2022	in dry/wet condition				ONLINE REPORT
Sr. No. Mark*		Casting Date* Size				Wet Weight	Dry Weight	Area of X-Section	Ultimate Ioad	Ultimate Stress	Absorpti	Remarks
		DD	MM	ΥΥΥΥ	(in)	(Kg/ gms)	(Kg/ gms)	(Sq. in)	(Imp.Tons)	(psi)	on (%)	
1	S				8.7 x 4.3 x 2.9	3685	3310	37.41	39	2335	11.33	
2	S				8.8 x 4.3 x 3	3540	3145	37.84	45	2664	12.56	
3	S				8.7 x 4.3 x 3	3505	3100	37.41	37	2215	13.06	
4	S				8.8 x 4.4 x 3.1	3695	3310	38.72	69	3992	11.63	
5	S				8.6 x 4.3 x 2.9	3455	3175	36.98	57	3453	8.82	
6	S				8.5 x 4.3 x 3	3625	3255	36.55	35	2145	11.37	
7	S				8.6 x 4.3 x 2.9	3605	3225	36.98	39	2362	11.78	
8	S				8.5 x 4 <mark>.1 x 2.8</mark>	3465	3100	34.85	53	3407	11.77	
9	S				8.7 x 4.3 x 2.9	3565	3190	37.41	53	3173	11.76	
10	S				8.7 x 4.2 x 3	3720	3225	36.54	45	2759	15.35	
11												
12												
13												
14												
15												
16												
Witness	ed by:	<u>.</u>	•			·	·					

Results can also be seen on website https://civil.uet.edu.pk/concrete-laboratory-reports1/

1. * as engraved on the specimens (if any)

2. ** BS3921 requires average of ten clay brick samples for crushing strength and water absorption

3. *** BS5328 requires mean of two cube sample strength at 28 days as characteristic strength

4. **** ACI318-08 requires mean of two sample (6"diax12" cylinder) strength at 28 days as compressive strength

 $\underline{\textbf{Note:}}$ Above results pertain to the unsealed samples supplied to the laboratory